

# SE140 & SE140BL

## 140° T<sub>g</sub> EPOXY PREPREG SYSTEM

**SE140 & SE140BL are designed for manufacture of complex composite components which are typically manufactured in the automotive, motorsport and sporting goods sectors.**

The cured resin has a good balance of laminate strength, toughness and environmental performance making it a very versatile product. SE140 & SE140BL are a flow controlled prepreg, which has been optimised for fast cure under high consolidation pressures but can also be cured under vacuum pressure if required. The prepreg resin provides suitable tack to adhere to metal and composite tools but is still easy to reposition at ambient temperatures.

SE140BL is a black pigmented version of SE140, containing a low level of black pigment to enhance the appearance of the resin by giving it a translucent black finish.



- Optimized prepreg for compression molding and autoclave cure
- Flow-controlled resin for improved surface finish
- Fast cure of 20 minute at 130-135°C (266-275°F)
- Oven and vacuum bag cure of 6 hours at 80°C (176°F)
- Toughened resin for improved mechanical properties

## INSTRUCTIONS FOR USE

SE140 & SE140BL are low tack prepreg and yet still offers high drape characteristics for precision laminating. It is possible to reposition when applied together but once pushed into place it will become difficult to separate. It will also self-adhere to a mould surface at 21°C (70°F), additional heat can be used to increase tack, but the product will be difficult to use in workshop temperatures above 23°C. SE 140 resin is a clear resin and is not filled, which helps to maintain good resin clarity for cosmetic applications. The resin will exhibit good UV and environmental weathering protection. However, like all epoxy resin prepregs over time the resin will gradually yellow with exposure to UV light, so a protective clear coat lacquer is recommended.

When manufacturing cosmetic carbon components, it is recommended that high consolidation pressure curing methods are used (autoclave or press). This will ensure no pinholes appear on the surface and give a repeatable finish for lacquering.

### AUTOCLAVE, PRESSURE BLADDER & VACUUM BAG PROCESSING

The mould should be treated with a high temperature release agent or film prior to lay-up. Place the layers of material into the mould in the same manner as a traditional prepreg. Overlaps are needed to ensure a continuous fibre distribution, the overlap distance should be in the region of 10-20mm.

Vacuum debulks may be needed to aid the placement of the layers, typically a 15-30 min debulking at 21°C (69°C) is used. A perforated release film and a breather mesh should be used in this operation to gain even vacuum over the part. Vacuum debulks will also reduce the amount of surface pin holes and voiding in the cured laminate when using a vacuum only cure.

For vacuum only -1bar cures a perforated release film should be used and for autoclave where the pressure is greater than +1bar a non-perforated release film is typically required.

### PRESS PROCESSING

The press perform or charge should be made from multiple plies stacked on top of each other. Depending on part complexity preforms can be made from either; rough shaping the material by hand, vacuum, or diaphragm forming methods. Woven and fabric preforms will not flow during pressing and therefore need to be net shape or larger.

The tooling used should have a closed or sealed cavity edge as the viscosity of the resin reduces during cure and needs to be contained within the cavity. If the tooling is open on the edge a reduced consolidation pressure will be achieved, and this will result in surface pin holes or dry surface fibres. An improved surface finish can be obtained by partially closing the tool and applying a vacuum before the upper tool contacts the prepreg. This vacuum step will remove trapped air before the mould contacts the prepreg. The controlled flow of SE 140 & SE140BL makes them more tolerant to pressing without vacuum or mould edge flow control, but generally a more repeatable surface finish is obtained with these features.

Pressing without vacuum is likely to result in a part with some minor porosity. Typical moulding pressures are between 10-20 bar (145 – 290 PSI) although higher pressures are also acceptable.


## PRODUCT INFORMATION

### AVAILABILITY

SE 140 & SE140BL are available in unidirectional carbon formats ranging in weight from 110 to 600g/m<sup>2</sup>, also woven or multiaxial reinforcements in carbon or glass from 100-660g/m<sup>2</sup>.

## PREPREG PROPERTIES

### RHEOLOGY DATA

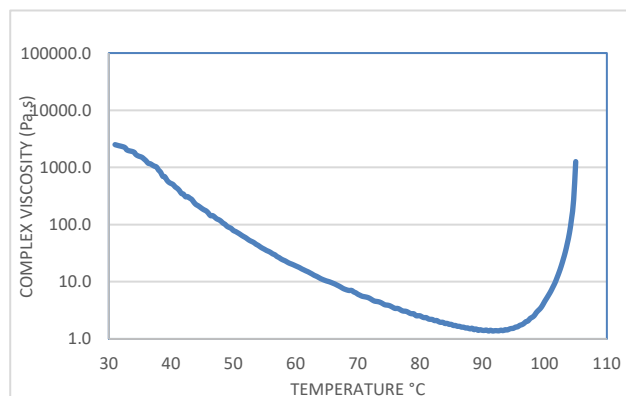

PROPERTY	UNITS	VALUE
Minimum viscosity	Pa.s (P)	1.4 (14)
Temperature at minimum viscosity	°C (°F)	92 (198)

## HOT WET PERFORMANCE

PROPERTY	CURE	CONDITIONING	UNITS	VALUE
Tg1 DMA	60 minutes at 140°C	14 days at 21°C	°C (°F)	140 (284)
Tg1 DMA	60 minutes at 140°C	24 hour immersion in 100°C water	°C (°F)	101 (213)

## CURE TIME AND TEMPERATURES

SE 140 & SE140BL offers flexible curing options and can be cured via autoclave, pressure bladder, press and vacuum processing methods.

## AUTOClave AND VACUUM PROCESSING CURE

PROPERTY	80°C CURE (176°F)	120°C CURE (248°F)	130°C CURE (266°F)	TEST METHOD
Processing method	Vacuum bag / Autoclave	Vacuum bag / Autoclave	Vacuum bag / Autoclave	
Typical ramp rate	0.3 – 2°C/minute	1 – 2°C/minute	1 – 2°C/minute	
Cure time	6 hrs	45 minutes	20 minutes	
Tg (DMA)	85-90°C (185-194°F)	125-130°C (257-266°F)	135-140°C (275-284°F)	ASTM D7028

## PRESS PROCESSING

The table below is a guide of flow and cure vs. temperature when using a hot in-hot out press process.

PROPERTY	125°C CURE (257°F)	130°C CURE (266°F)	135°C CURE (275°F)
Flow time	2:54	2:03	1:21
Cure conversion( 90%) mins:seconds	18:30	9:15	6:30
Cure conversion( 95%) mins:seconds	-	17:45	9:15
Cure conversion( 97.5%) mins:seconds	–		13:15

The tool should be shut before the recommended flow time to avoid pre-gelling or of the prepreg resin. Parts < 6mm thick have been processed without exothermic heat release problems using metal compression tooling to conduct heat away from both the A and B surfaces. Tests may be needed to check for exothermic heat release in thicker laminates. Excessive exotherm may discolour the resin.

Recommended press process, 1) Apply the charge to a 130-135C (266°F to 275°F) tool; 2) Partial close to apply a vacuum; 3) Begin final close 1min and 30seconds after the charge first contacts the hot tool; 4) Aim to have completed the tool close by 1min and 40 seconds; 5) Open the press and demold 15 minutes after the charge first contacts the hot tool.

Shorter cures can be achieved with increased cure temperature or with reduced levels of cure conversion, but this can result in deformed components after demold.

## PREPREG PROPERTIES

PROPERTY	UNITS	RC200T	RC245T/42%	RC380T	RC660T	TEST METHOD
Fabric style	-	0/90° Woven 2x2 twill	0/90° Woven 2x2 twill	0/90° Woven 2x2 twill	0/90° Woven 2x2 twill	-
Fabric areal weight	-	200	245	380	660	ASTM D3171
Fiber Type	-	3k Carbon	3k Carbon	12K Carbon	12K Carbon	-
Resin content	%	40	42	40	34	ASTM D3171 Method II
Nominal prepreg areal weight	g/m²	333	422	633	1000	ASTM D3171 Method II
Nominal cured ply thickness	mm	0.22	0.28	0.42	0.65	ASTM D792
Nominal cured density	Kg/m³	1500	1488	1500	1538	ASTM D3171 Method II

## CURED LAMINATE PROPERTIES

SE140 / RC200T woven carbon, 60 minutes at 140°C (284°F).

PROPERTY	SYMBOL	UNITS		SE140/RC200T (3k)		TEST METHOD
0° Tensile strength*	$\sigma_{T11}$	MPa	(ksi)	786	(114.0)	ISO527-4
0° Tensile modulus*	$E_{T11}$	GPa	(Msi)	70.8	(10.2)	ISO527-4
90° Tensile strength*	$\sigma_{T22}$	MPa	(ksi)	744	(107.9)	ISO527-4
90° Tensile modulus*	$E_{T22}$	GPa	(Msi)	68.6	(9.9)	ISO527-4
0° Compression strength*	$\sigma_{C11}$	MPa	(ksi)	777	(112.6)	SACMA SRM1-94
0° Compression modulus*	$E_{C11}$	GPa	(Msi)	59.6	(8.6)	SACMA SRM1-94
90° Compression strength*	$\sigma_{C22}$	MPa	(ksi)	719	(104.2)	SACMA SRM1-94
90° Compression modulus*	$E_{C22}$	GPa	(Msi)	60.7	(8.8)	SACMA SRM1-94
0° Flexural strength	$\sigma_F$	MPa	(ksi)	913	(132)	ISO 14125
0° Flexural modulus	EF11	GPa	(Msi)	54.3	(7.8)	ISO 14125
90° Flexural strength	$\sigma_F$	MPa	(ksi)	669	(97.03)	ISO 14125
90° Flexural modulus	EF11	GPa	(Msi)	55.8	(8.0)	ISO 14125
0° ILSS	$T_{ILSS}$	MPa	(ksi)	80	(11.6)	ISO 14130
Glass transition DMA	$T_{g1}$	°C	(°F)	140	(284)	ISO14125

\* Normalised to 55%  $V_f$

SE140 / RC245T woven carbon, vacuum cure of 2°C/min to 130°C (266°F), 130°C (266°F) dwell for 20 minutes.

PROPERTY	SYMBOL	UNITS		SE140/RC245T (3k)		TEST METHOD
0° Tensile strength*	$\sigma_{T11}$	MPa	(ksi)	620	(89.9)	ISO527-4
0° Tensile modulus*	$E_{T11}$	GPa	(Msi)	63.8	(9.3)	ISO527-4
Poissons ratio	$\nu_{12}$	-	-	0.05	(0.05)	ISO527-4
90° Tensile strength*	$\sigma_{T22}$	MPa	(ksi)	626	(90.7)	ISO527-4
90° Tensile modulus*	$E_{T22}$	GPa	(Msi)	62.8	(9.1)	ISO527-4
Poissons ratio	$\nu_{21}$	-	-	0.05	(0.1)	ISO527-4
0° Compression strength*	$\sigma_{C11}$	MPa	(ksi)	703	(102)	SACMA SRM1-94
0° Compression modulus*	$E_{C11}$	GPa	(Msi)	60.3	(8.7)	SACMA SRM1-94
90° Compression strength*	$\sigma_{C22}$	MPa	(ksi)	680	(98.7)	SACMA SRM1-94
90° Compression modulus*	$E_{C22}$	GPa	(Msi)	60.5	(8.8)	SACMA SRM1-94
0° Flexural strength	$\sigma_F$	MPa	(ksi)	828	(120)	ISO 14125
0° Flexural modulus	EF11	GPa	(Msi)	50.7	(7.4)	ISO 14125
90° Flexural strength	$\sigma_F$	MPa	(ksi)	823	(119)	ISO 14125
90° Flexural modulus	EF11	GPa	(Msi)	51.3	(7.4)	ISO 14125
0° ILSS	$T_{ILSS}$	MPa	(ksi)	75.7	(11.0)	ISO 14130
Glass transition DMA	$T_{g1}$	°C	(°F)	134	(273)	ISO14125

\* Normalised to 60%  $V_f$

SE140 / RC380T woven carbon, vacuum cure of 2°C/min to 130°C (266°F), 130°C (266°F) dwell for 20 minutes.

PROPERTY	SYMBOL	UNITS		SE140/RC380T (12k)		TEST METHOD
0° Tensile strength*	$\sigma_{T11}$	MPa	(ksi)	936	(135.7)	ISO527-4
0° Tensile modulus*	$E_{111}$	GPa	(Msi)	66.6	(9.6)	ISO527-4
0° Compression strength*	$\sigma_{C11}$	MPa	(ksi)	679	(98.4)	SACMA SRM1-94
0° Compression modulus*	$E_{c11}$	GPa	(Msi)	59	(8.5)	SACMA SRM1-94
0° Flexural strength	$\sigma_F$	MPa	(ksi)	990	(143.5)	ISO 14125
0° Flexural modulus	EF11	GPa	(Msi)	55	(7.9)	ISO 14125
0° ILSS	$\bar{T}_{ILSS}$	MPa	(ksi)	56	(8.1)	ISO 14130
Glass transition $T_{g1}$ DMA	$T_{g1}$	°C	(°F)	134	(273)	ISO14125

\* Normalised to 55%  $V_f$

SE140 / RC660T 12K woven carbon, vacuum cure of 2°C/min to 130°C (266°F), 130°C (266°F) dwell for 20 minutes.

PROPERTY	SYMBOL	UNITS		SE140/RC660T		TEST METHOD
0° Tensile strength*	$\sigma_{T11}$	MPa	(ksi)	762	(122)	ISO527-4
0° Tensile modulus*	$E_{111}$	GPa	(Msi)	60.4	(8.76)	ISO527-4
0° Compression strength*	$\sigma_{C11}$	MPa	(ksi)	506	(73.4)	SACMA SRM1-94
0° Compression modulus*	$E_{c11}$	GPa	(Msi)	55.5	(8.05)	SACMA SRM1-94
0° Flexural strength	$\sigma_F$	MPa	(ksi)	577	(83.7)	ISO 14125
0° Flexural modulus	EF11	GPa	(Msi)	59.3	(8.6)	ISO 14125
±45° In-plane shear strength	$\bar{T}_{120.05}$	MPa	(ksi)	63.3	(9.18)	ISO 14129
±45° In-plane shear modulus	$G_{12}$	GPa	(Msi)	4.61	(0.67)	ISO 14129
±45° In-plane shear strength	$\bar{T}_{12\ max}$	MPa	(ksi)	92.1	(13.4)	ISO 14129
±45° In-plane shear Poisson's Ratio	$V_{12}$	-	-	0.77		ISO 14129
0° ILSS	$\bar{T}_{ILSS}$	MPa	(ksi)	51	(6.8)	ISO 14130
Glass transition DMA	$T_{g1}$	°C	(°F)	140°C	(284)	ISO14125

\* Normalised to 55%  $V_f$

SE140BL/ HEC300 unidirectional carbon, vacuum cure of 2°C/min to 130°C (266°F), 130°C (266°F) dwell for 60 minutes.

PROPERTY	SYMBOL	UNITS		SE140BL/HEC300		TEST METHOD
0° Tensile strength*	$\sigma_{T11}$	MPa	(ksi)			ISO527-4
0° Tensile modulus*	$E_{111}$	GPa	(Msi)			ISO527-4
0° Compression strength*	$\sigma_{C11}$	MPa	(ksi)			SACMA SRM1-94
0° Compression modulus*	$E_{c11}$	GPa	(Msi)			SACMA SRM1-94
0° Flexural strength	$\sigma_F$	MPa	(ksi)			ISO 14125
0° Flexural modulus	EF11	GPa	(Msi)			ISO 14125
90° Tensile strength*	$\sigma_{T22}$	MPa	(ksi)			ISO 14129
90° Tensile modulus*	$E_{122}$	GPa	(Msi)			ISO 14129
90° Compression strength*	$\sigma_{C22}$	MPa	(ksi)			ISO 14129
90° Compression modulus*	$E_{c22}$	GPa	(Msi)			ISO 14129
0° ILSS	$\bar{T}_{ILSS}$	MPa	(ksi)			ISO 14130
Glass transition DMA	$T_{g1}$	°C	(°F)	121		ISO14125

SE140 / RF300T woven flax fabric, Press molded at 12Bar pressure, 135°C (275°F) for 15 minutes.

PROPERTY	SYMBOL	UNITS		SE140/RC245T		TEST METHOD
0° Tensile strength	$\sigma_{T11}$	MPa	(ksi)	167	(24.2)	ISO527-4
0° Tensile modulus	$E_{t11}$	GPa	(Msi)	12.7	(1.80)	ISO527-4
0° Compression strength	$\sigma_{C11}$	MPa	(ksi)	166	(24.0)	SACMA SRM1-94
0° Compression modulus	$E_{c11}$	GPa	(Msi)	12.0	(1.70)	SACMA SRM1-94
0° Flexural strength	$\sigma_F$	MPa	(ksi)	166	(24.1)	ISO 14125
0° Flexural modulus	$E_{F11}$	GPa	(Msi)	12.7	(1.84)	ISO 14125
0° ILSS	$\bar{T}$ ILSS	MPa	(ksi)	18.9	(2.80)	ISO 14130
Glass transition $T_{g1}$ DMA	$T_{g1}$	°C	(°F)	132	(269)	ISO14125

Test data has not been normalised by fiber volume fraction. Future testing is not guaranteed to give exactly the same values. Engineers should account for variability when choosing their design allowable properties.

#### TRANSPORT AND STORAGE

STORAGE TEMPERATURE	UNITS	VALUE
-18°C (0°F)	Months	24
+18-20°C (64-68°F)	Weeks	4

To maximise the de-frosted shelf life of the material it is beneficial to maintain a cool working environment. When not in use SE140 products should be maintained at -18°C (0°F).

## HEALTH AND SAFETY

The following points must be considered:

1. Skin contact must be avoided by wearing protective gloves. Gurit recommends the use of disposable nitrile gloves for most applications. The use of barrier creams is not recommended, but to preserve skin condition a moisturizing cream should be used after washing.
2. Protective clothing should be worn when mixing, laminating or sanding. Contaminated work clothes should be thoroughly cleaned before re-use.
3. Eye protection should be worn if there is a risk of resin, hardener, solvent or dust entering the eyes. If this occurs flush the eye with water for 15 minutes, holding the eyelid open, and seek medical attention.
4. Ensure adequate ventilation in work areas. Respiratory protection should be worn if there is insufficient ventilation. Solvent vapors should not be inhaled as they can cause dizziness, headaches, loss of consciousness and can have long term health effects.
5. If the skin becomes contaminated, then the area must be immediately cleansed. The use of resin-removing cleansers is recommended. To finish, wash with soap and warm water. The use of solvents on the skin to remove resins etc must be avoided.

Washing should be part of routine practice:

- before eating or drinking
- before smoking & vaping
- before using the lavatory
- after finishing work

6. The inhalation of sanding dust should be avoided and if it settles on the skin then it should be washed off. After more extensive sanding operations a shower/bath and hair wash is advised.

Gurit produces a separate full Safety Data Sheet for all hazardous products. Please ensure that you have the correct SDS to hand for the materials you are using before commencing work.

## NOTICE

All advice, instruction or recommendation is given in good faith but the selling Gurit entity (the Company) only warrants that advice in writing is given with reasonable skill and care. No further duty or responsibility is accepted by the Company. All advice is given subject to the terms and conditions of sale (the Conditions) which are available on request from the Company or may be viewed at Gurit's Website: [www.gurit.com/terms-and-conditions.aspx](http://www.gurit.com/terms-and-conditions.aspx)

The Company strongly recommends that Customers make test panels in the final process conditions and conduct appropriate testing of any goods or materials supplied by the Company prior to final use to ensure that they are suitable for the Customer's planned application. Such testing should include testing under conditions as close as possible to those to which the final component may be subjected. The Company specifically excludes any warranty of fitness for purpose of the goods other than as set out in writing by the Company. Due to the varied nature of end-use applications, the Company does, in particular, not warrant that the test panels in the final process conditions and/or the final component pass any fire standards.

The Company reserves the right to change specifications and prices without notice and Customers should satisfy themselves that information relied on by the Customer is that which is currently published by the Company on its website. Any queries may be addressed to the Technical Services Department.

Gurit is continuously reviewing and updating literature. Please ensure that you have the current version by contacting your sales contact and quoting the revision number in the bottom left-hand corner of this page.

## CONTACT INFORMATION

Please see local contact information at [www.gurit.com](http://www.gurit.com)

## 24-HOUR CHEMICAL EMERGENCY NUMBER

For advice on chemical emergencies, spillages, fires or exposures:

Europe	+44 1273 289451
Americas	+1 646 844 7309
APAC	+65 3158 1412

[customer.support@gurit.com](mailto:customer.support@gurit.com)

[www.gurit.com](http://www.gurit.com)

All trademarks used or mentioned in this document are protected by law.